



■ KNEE

Autologous meniscus fragments embedded in atelocollagen gel enhance meniscus repair in a rabbit model

**N. Matsubara,
T. Nakasa,
M. Ishikawa,
T. Tamura,
N. Adachi**

From Hiroshima
University, Hiroshima,
Japan

Aims

Meniscal injuries are common and often induce knee pain requiring surgical intervention. To develop effective strategies for meniscus regeneration, we hypothesized that a minced meniscus embedded in an atelocollagen gel, a firm gel-like material, may enhance meniscus regeneration through cell migration and proliferation in the gel. Hence, the objective of this study was to investigate cell migration and proliferation in atelocollagen gels seeded with autologous meniscus fragments *in vitro* and examine the therapeutic potential of this combination in an *in vivo* rabbit model of massive meniscus defect.

Methods

A total of 34 Japanese white rabbits (divided into defect and atelocollagen groups) were used to produce the massive meniscus defect model through a medial patellar approach. Cell migration and proliferation were evaluated using immunohistochemistry. Furthermore, histological evaluation of the sections was performed, and a modified Pauli's scoring system was used for the quantitative evaluation of the regenerated meniscus.

Results

In vitro immunohistochemistry revealed that the meniscus cells migrated from the minced meniscus and proliferated in the gel. Furthermore, histological analysis suggested that the minced meniscus embedded in the atelocollagen gel produced tissue resembling the native meniscus *in vivo*. The minced meniscus group also had a higher Pauli's score compared to the defect and atelocollagen groups.

Conclusion

Our data show that cells in minced meniscus can proliferate, and that implantation of the minced meniscus within atelocollagen induces meniscus regeneration, thus suggesting a novel therapeutic alternative for meniscus tears.

Cite this article: *Bone Joint Res* 2021;10(4):xxx–xxx.

Keywords: Atelocollagen, Meniscus, Rabbit model of massive meniscus defect

Article focus

- Cell migration and proliferation of minced meniscus in atelocollagen scaffold were evaluated.
- Meniscus regeneration following implantation of the minced meniscus into a massive meniscus defect rabbit model was investigated.

Key messages

- Cells from the minced meniscus proliferated in atelocollagen gel.

- Implantation of minced meniscus induced meniscus regeneration.

Strengths and limitations

- Atelocollagen as a scaffold for implantation of the minced meniscus is easy to use and effective.
- Mechanical properties of the regenerated tissue were not evaluated, and results in humans may be different from those in rabbits.

Correspondence should be sent to Norimasa Matsubara; email: matunoriseikei@yahoo.co.jp

doi: 10.1302/2046-3758.104.BJR-2019-0359.R2

Bone Joint Res 2021;10(4):xxx–xxx.

Introduction

Meniscal injuries are common and often induce knee pain and dysfunction, necessitating surgical treatment.¹ In particular, meniscal tears in avascular regions do not heal completely due to a lack of blood supply; thus, partial meniscectomy is performed to improve symptoms.² For large radial or severe degenerative tears, partial meniscectomy often results in massive meniscus defects frequently leading to osteoarthritis of the knee.³ Therefore, novel techniques for regenerating an injured meniscus are needed to prevent joint degeneration after a massive loss of the meniscus.

To achieve meniscus regeneration, cell therapy and/or tissue engineering techniques have been evaluated in both animal studies and clinical trials, and stem cell therapy has been recognized as a promising strategy.^{4,5} Multipotent mesenchymal stem cells (MSCs) have been used for meniscal regeneration. They offer several advantages, such as easy isolation and expansion, and multidifferentiation ability.⁶⁻¹⁰ Other cells, including fibrochondrocytes, chondrocytes, and myoblasts, have also been used for meniscus regeneration in animal models.¹¹⁻¹⁴ Although these cell therapies have produced desirable results, they require cell isolation and culture, and typically involve a two-step surgery. Thus, the cell source and implantation technique should be considered to develop a streamlined one-step surgery approach.

In cartilage repair, the use of cartilage fragments has attracted considerable attention.^{15,16} This involves a one-step procedure known as the cartilage autograft implantation system or particulated juvenile allograft cartilage, and good clinical results have been reported.¹⁷ Chondrocytes have been shown to migrate with this method from the cartilage fragments, and subsequently proliferate to produce the cartilage matrix.^{18,19} These results demonstrate that cell isolation from tissues and culture for implantation is less advantageous for tissue repair. Similarly, the advantages of minced meniscus over cultured cells for meniscus regeneration have been highlighted in animal models.^{20,21} Implantation of juvenile allografts and minced fragments have been reported to promote the healing of an avascular meniscal injury in an organ culture model.²⁰ Implantation of autologous meniscal fragments wrapped with a fascia sheath into a meniscal defect significantly enhanced fibrocartilage regeneration in rabbits.²¹ Therefore, in order to develop a more effective procedure for meniscus regeneration, the combination of the minced meniscus and a scaffold should be examined.

Atelocollagen, a firm gel-like material, is generated from bovine type I collagen in which the telopeptides on the peptide chains, which are antigenic determinants, are removed. This 3D structure is suitable as a scaffold for cell culture.²² We hypothesized that minced meniscus embedded in atelocollagen gel would enhance meniscus regeneration through meniscus cell migration and proliferation in the gel. This study aimed to investigate

cell migration and proliferation in atelocollagen gel seeded with autologous meniscus fragments *in vivo*, and examine the therapeutic potential of minced meniscus combined with atelocollagen gel for tissue regeneration in a massive meniscus defect in a rabbit model *in vivo*.

Methods

Animals. A total of 34 Japanese white rabbits weighing between 2.5 kg and 3.2 kg were used (45 knees for *in vivo* study (15 knees per group) and 22 knees for *in vitro* study). Surgery was performed under general anaesthesia by intramuscular injection of xylazine (3 mg/kg) and ketamine (10 mg/kg). Through a medial parapatellar approach, the patella was dislocated laterally, and the medial meniscus was exposed. The anterior half of the medial meniscus was then excised to produce the massive meniscus defect model.²² Resected meniscus tissue was manually minced to pieces < 1 mm³ in a petri dish using a scalpel as reported previously.²³ In the minced meniscus group (n = 5), 25 mg of the minced meniscus was mixed with 100 µl of atelocollagen, placed in a culture dish to form a firm gel for 30 minutes, and then implanted in the meniscus defect (Supplementary Figure a). In the atelocollagen group, 100 µl of atelocollagen was implanted in the defect sites (n = 5). Meniscus defects in the defect group remained empty, and the resected meniscus tissues from this group were used for the *in vivo* study (n = 5). Thereafter, the joint capsule and skin were closed. The rabbits were killed at eight, 12, and 16 weeks using sodium pentobarbital, and the medial meniscus was harvested. The tissues were fixed using 4% paraformaldehyde phosphate-buffered solution (PFA) (Wako Pure Chemical Industries, Japan) at 4°C overnight, embedded in paraffin, and cut into 4 µm sections. All procedures were performed according to the Guidelines for Animal Experimentation at Hiroshima University with the approval of the Committee of Research Facilities for Laboratory Animal Sciences, Graduate School of Biomedical Sciences, Hiroshima University.

Cell culture. Meniscus tissues from the anterior half of the medial meniscus in the defect group were manually minced in phosphate-buffered saline (PBS) to pieces < 1 mm³ with a surgical scalpel, washed in PBS three times, and embedded in atelocollagen gel. To examine the effect of the volume of the minced meniscus on cell migration and proliferation, the tissues were divided into three groups, in which 25 mg (group A), 50 mg (group B), or 125 mg (group C) of the minced meniscus was embedded in 100 µl atelocollagen. The composites were placed on the culture dish and allowed to form a firm gel for 30 minutes, followed by the addition of Dulbecco's Modified Eagle's Medium (DMEM) (Gibco BRL, USA) with 10% fetal bovine serum (Sigma-Aldrich, USA) and 1% antibiotics (penicillin, streptomycin, and fungizone) (BioWhittaker, USA). The dishes were incubated in a humidified atmosphere with 5% CO₂ at 37°C and cultured for three weeks. The medium was changed every three days. At three

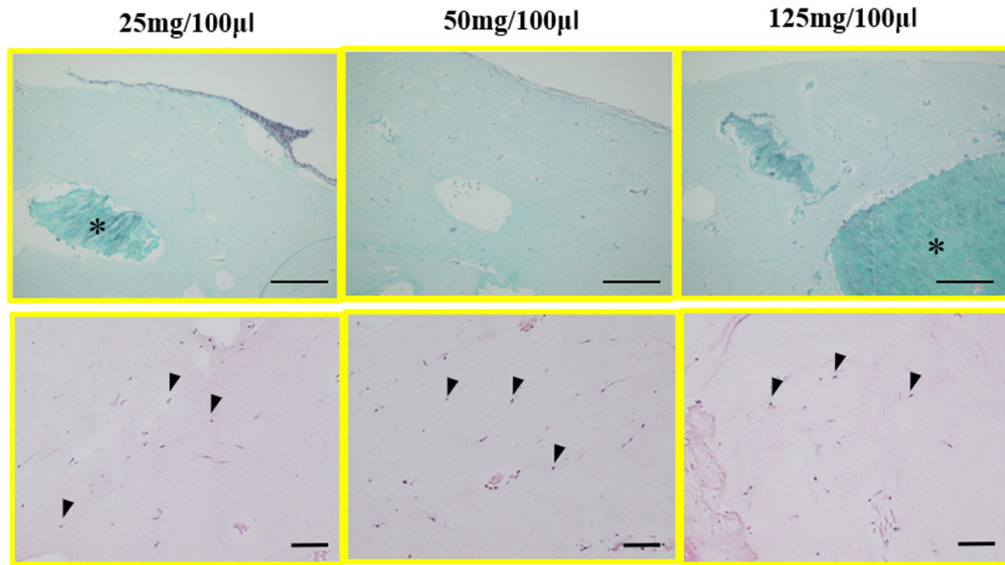


Fig. 1

Upper section: Safranin-O/Fast green staining in each group; asterisks denote minced meniscus. Scale = 300 μm . Lower section: haematoxylin and eosin staining in each group. Arrowheads indicate the cells in the atelocollagen gel, scale = 100 μm . 25 mg, 50 mg, and 125 mg indicate the volume of minced meniscus embedded in 100 μl of atelocollagen.

weeks, the composites were fixed in 4% PFA at 4°C overnight. Samples were embedded in paraffin and cut into 5 μm sections along the axial plane. Sections were stained using Haematoxylin and Eosin (HE) and Safranin-O for histological assessment.

Immunohistochemistry in vitro. Sections were incubated with antigen retrieval reagent (Immunoactive; Matsunami Glass, Japan) for one hour, followed by 0.3% H_2O_2 for 30 minutes, normal blocking serum for 30 minutes, and primary antibody against Ki67 (Cell Signalling Technology, USA) overnight at 4°C. The next day, the sections were visualized using the avidin-biotin system (Vectastatin Elite ABC Mouse IgG Kit; Vector Laboratories, USA) and 3,3'-diaminobenzidine (Peroxidase Substrate Kit; Vector Laboratories) according to the manufacturer's instructions. To assess cell proliferation, the total number of cells, the number of cells stained by the Ki67 antibody, and the ratio of stained cells to total cells were determined in nine randomly selected sections of 300 μm^2 in atelocollagen areas.

Macroscopic evaluation. The tibial plateaus were photographed, and the sizes of the medial and lateral meniscus were measured using ImageJ software (version 1.43, National Institutes of Health, USA). The ratio of the medial meniscus area to the lateral meniscus area was calculated as previously described.²³

Histological evaluation. Sections were stained using HE, Safranin-O/Fast green, and Toluidine blue. A modified Pauli's scoring system was used^{24,25} for the quantitative evaluation of the regenerated meniscus, performed in a blind manner by two orthopaedic surgeons (TS and HN). The modified scoring system consists of four sections: morphology of the regenerated meniscus, cellularity of the chondrocytes, collagen fibre organization, and matrix

staining. The scoring of each section was 6, 3, 3, and 3 points, respectively.

Statistical analysis. Scheffe's F-test was used for comparison between groups in the in vivo experiment and comparison between the respective groups in the in vivo experiment at each timepoint. Results with a p-value < 0.05 were considered statistically significant.

Results

To examine meniscus cell migration and proliferation in atelocollagen gel, the cells in the gel seeded with three different doses were quantified. Migrated and proliferated cells were observed in the gel and on the surface of the composites in all groups (Figure 1). Areas (300 $\mu\text{m} \times 300 \mu\text{m}$) were randomly selected, and the average cell number was calculated. The mean number of cells in groups A, B, and C was 6.7 (standard deviation (SD) 4.5), 6.0 (SD 5.6), and 4.4 (SD 3.2), respectively. Although group A produced the highest number of cells, there was no significant difference in the number of cells among the groups. In the immunological analysis, areas (300 $\mu\text{m} \times 300 \mu\text{m}$) were randomly selected, and the mean positive cell number was calculated. Immunohistochemistry revealed a high number of Ki67-positive cells both in the gel and minced meniscus (Figure 2a and Supplementary Figure b). The mean total number of Ki67-positive cells per field of view in groups A, B, and C was 5.0 (SD 4.3), 4.6 (SD 5.5), and 2.8 (SD 3.2), respectively ($p > 0.05$) (Figure 2b). The ratio of Ki67-positive cells to total cells was 76% \pm 5.4%, 75% \pm 5.7%, and 62% \pm 9.9%, respectively ($p > 0.05$) (Figure 2c). The mean meniscal cell count from one fragment of minced meniscus per 10 mg was 11.3×10^4 in 3D culture and 7.5×10^4 cells in 2D

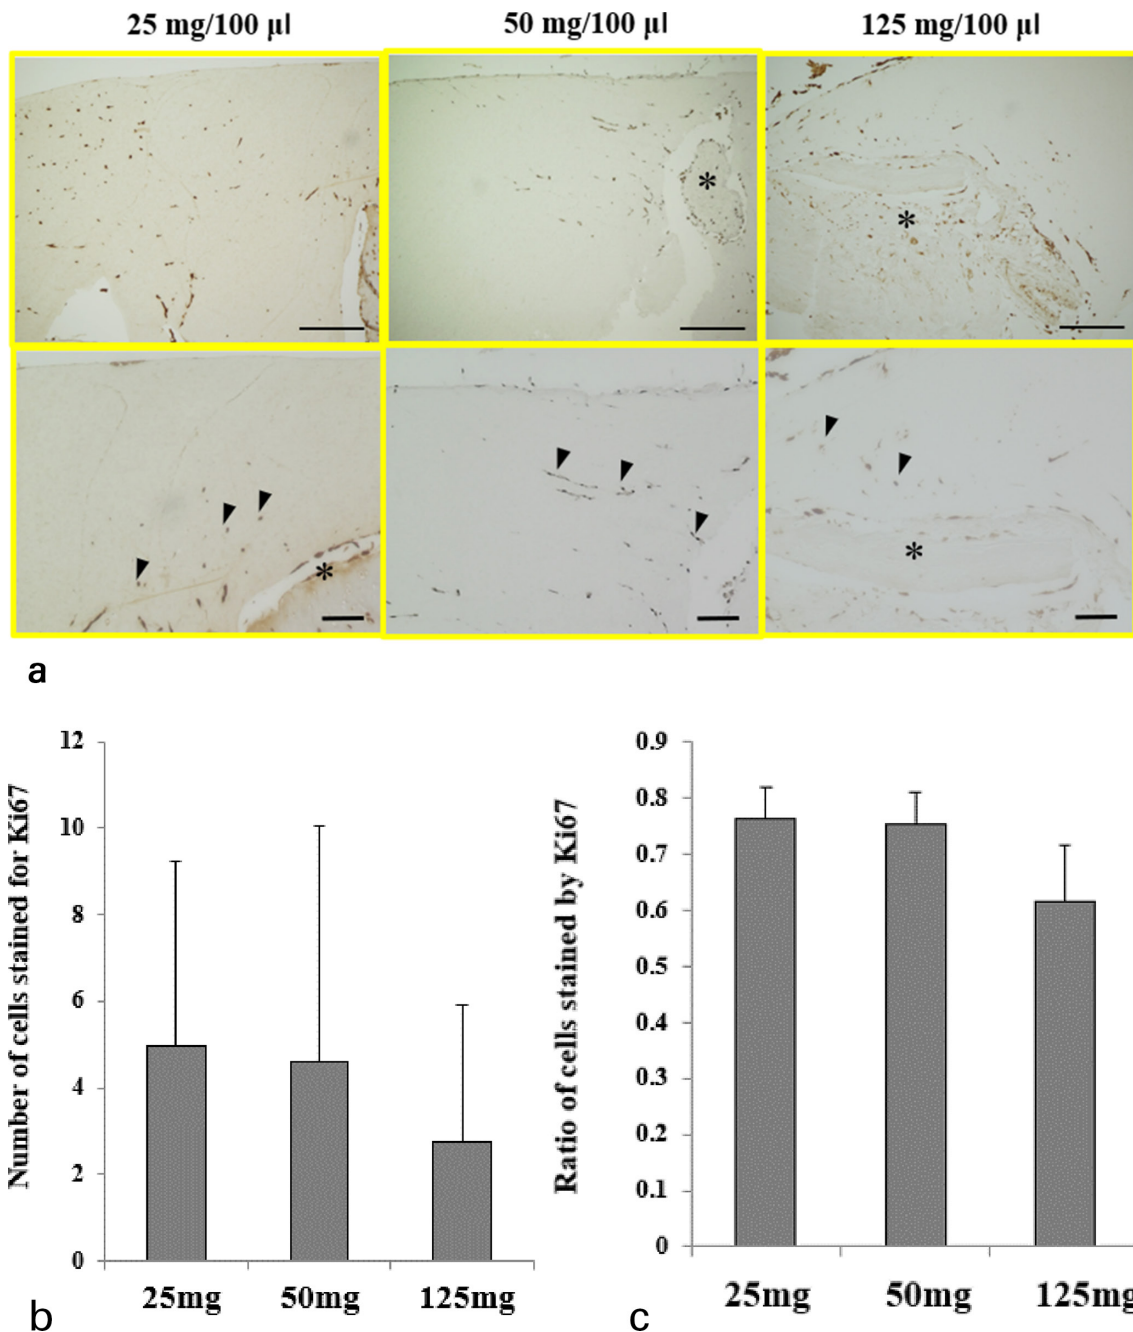


Fig. 2

a) Immunohistochemistry for Ki-67 in each group; asterisks denote minced cartilage. Arrowheads indicate the cell stained for Ki-67 in the atelocollagen gel; asterisks denote minced cartilage; thin bar = 300 μ m, thick bar = 100 μ m. The quantities of 25 mg, 50 mg, and 125 mg indicate the volume of minced meniscus embedded in 100 μ l of atelocollagen. b) Number of cells stained by Ki-67 for each group. There is no significant difference between groups. The quantities of 25 mg, 50 mg, and 125 mg indicate the volume of minced meniscus embedded in 100 μ l of atelocollagen. c) The ratio of cells stained by Ki-67 for each group. There is no significant difference between groups. The quantities of 25 mg, 50 mg, and 125 mg indicate the volume of minced meniscus embedded in 100 μ l of atelocollagen.

culture (Supplemental Figure c). Using a three-lineage differentiation assay, it was confirmed that the meniscus cells did not differentiate into osteoblasts and adipocytes. However, they formed a pellet with positive staining with Safranin O. Chondrocytes were also observed in the pellet, suggesting that the meniscus cells were capable of chondrogenesis (Supplemental Figure 4).

No adverse effects were seen after implantation of the minced meniscus. In the defect group, the meniscus defect remained unchanged at 12 weeks. In the minced meniscus group, the presence of the transplanted minced meniscus in the meniscus defect was first confirmed by MRI at 12 weeks (Supplementary Figure e). Based on gross appearance, the defect group exhibited an empty

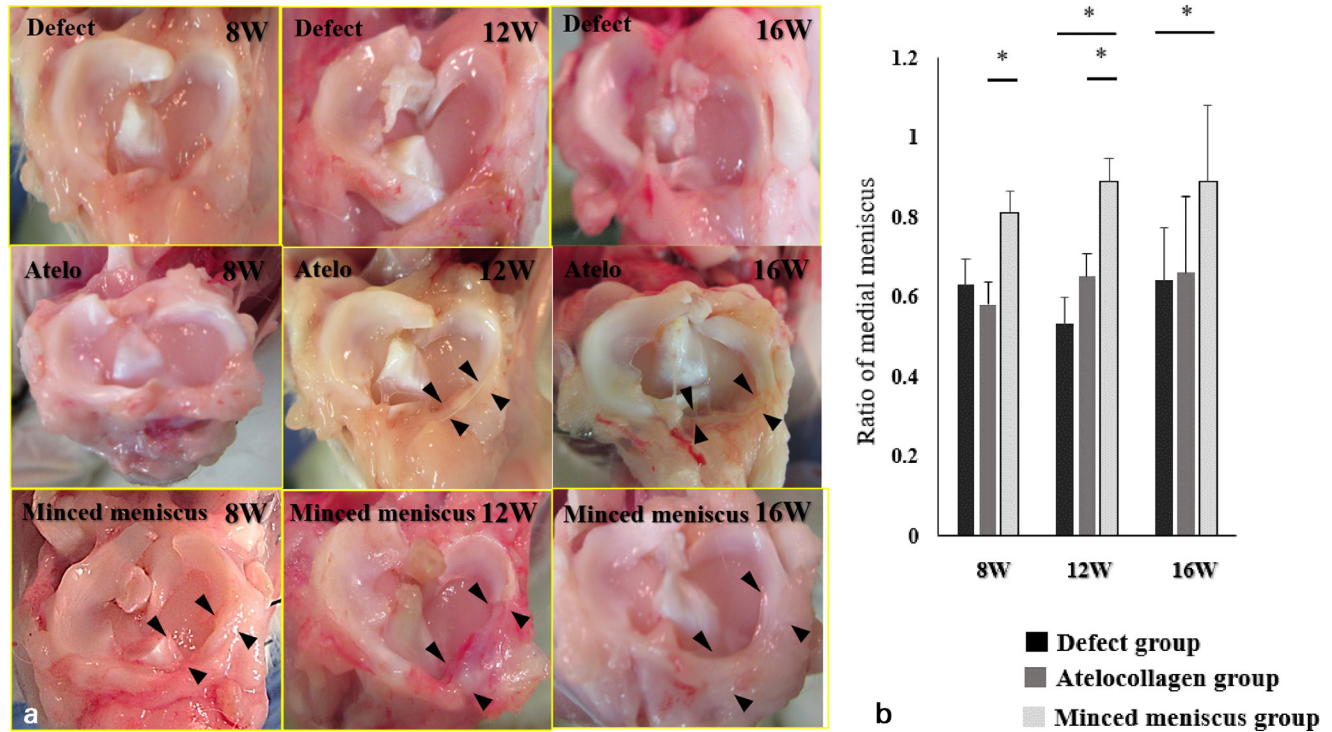


Fig. 3

a) Upper sections (defect groups). The scar tissue can be seen at eight weeks, although the tissues are incomplete. Middle sections represent the atelocollagen groups. Steady but thin tissues can be seen at 12 weeks. Lower sections represent minced meniscus groups. Steady and complete tissues can be seen at 16 weeks. Arrowheads indicate regenerated tissues. b) The ratio of the regenerated medial meniscus for both groups was defined as that of the area of the regenerated medial meniscus to the lateral meniscus. The ratios of the regenerated medial meniscus are better in the minced meniscus groups than in the other groups ($p < 0.05$).

meniscus defect at eight weeks. A small amount of scar tissue appeared at 12 weeks, and these scars expanded to link the meniscus defect. The atelocollagen group showed bridging formation, however the defect area was not filled with a regenerative tissue wall at 16 weeks. By contrast, the minced meniscus group showed continuity of the meniscus defect and soft tissue at eight weeks, and this soft tissue formed a solid meniscus-like tissue (Figure 3a). The ratios of the regenerated tissue in the defect, atelocollagen, and minced meniscus groups were $64.6\% \pm 6.5\%$, $57.7\% \pm 11.1\%$, and $81.4\% \pm 12.5\%$ at 8 weeks, $54.0\% \pm 3.0\%$, $64.5\% \pm 10.3\%$, and $88.6\% \pm 5.7\%$ at 12 weeks, and $63.7\% \pm 13.4\%$, $65.9\% \pm 7.8\%$, and $88.9\% \pm 19.1\%$ at 16 weeks, respectively. Furthermore, the ratio in the minced meniscus group was significantly higher than that in the atelocollagen group at eight weeks, in both the groups at 12 weeks, and in the defect group at 16 weeks (Figure 3b).

Histological analysis revealed that the surfaces of the defect and atelocollagen groups were rough, and the cells were not well distributed including the lamellar layer of both the femoral and tibial sides, however the surfaces of the minced meniscus group were almost smooth, and the cells were well distributed at eight weeks. The regenerated tissues of the defect and atelocollagen group were less filled with chondrocyte-like cells and less stained by Safranin-O than those of the minced meniscus group.

(Figure 4a). The regenerated tissues were not strongly stained with Toluidine blue in the defect and atelocollagen model, but they were strongly stained at 12 weeks in the minced meniscus group. (Figure 4b). The regenerated tissue of the minced meniscus group, but not of the defect and atelocollagen groups was strongly stained by Safranin-O (Figure 4c). The modified Pauli's score based on Toluidine blue staining was significantly higher in the minced meniscus group than that in the defect group at all timepoints (eight weeks: 9.0 (SD 3.9) vs 2.0 (SD 1.6); $p < 0.05$); 12 weeks: 9.0 (SD 4.0) vs 2.6 (SD 3.0), $p < 0.05$; 16 weeks: 12.0 (SD 0.4) vs 2.6 (SD 1.2); $p < 0.05$) (Figure 4d). Further, the modified Pauli's score was significantly higher in the minced meniscus group than that in the atelocollagen group at eight and 16 weeks (eight weeks: 9.0 (SD 3.9) vs 3.2 (SD 1.5), $p < 0.05$; 12 weeks: 9.0 (SD 4.0) vs 3.8 (SD 4.3), $p > 0.05$; 16 weeks: 12.0 (SD 0.4) vs 5.4 (SD 2.8), $p < 0.05$) (Figure 4d).

To examine the effects of stem/progenitor cells in meniscus regeneration, immunohistochemistry using CD44 and CD271 staining was performed. No CD44 and CD271 positive cells were seen in any of the specimens at eight weeks (Supplementary Figure f).

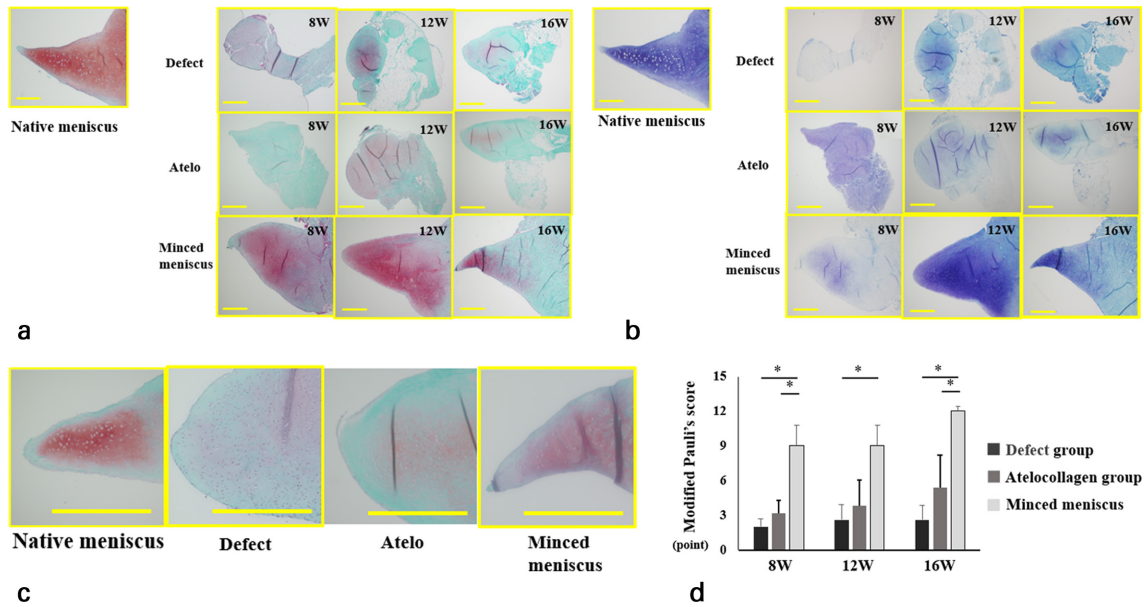


Fig. 4

a) Safranin-O/Fast green staining: representative pictures of each group at eight, 12, and 16 weeks. The left figure shows native meniscus. b) Toluidine blue staining: representative pictures of each group at eight, 12, and 16 weeks. The left figure shows native meniscus. c) Regenerated meniscus tissues at 16 weeks. Minced meniscus models presented more similar morphological and histological structures to the native meniscus than the other groups. d) Modified Pauli's scoring system for minced meniscus models is significantly better than that for the other groups ($p < 0.05$).

Discussion

In this study, we found that minced meniscus embedded in atelocollagen gel exhibits high cell migration and proliferation in vivo, and implantation of the same produces tissue resembling the native meniscus tissue in vivo. Tissue engineering has attracted significant attention for meniscus regenerative treatment.²⁶ A variety of cells, including meniscal cells, chondrocytes, and MSCs derived from bone marrow, fat tissue, or synovium, have been used.²⁷⁻³⁰ However, there is no consensus regarding the best cell resource for meniscal regeneration. Desirable results were reported in experiments using MSCs as a cell source, but it is not clear whether MSCs differentiate into meniscus cells due to a lack of markers for meniscal genes. There are some reports on the use of minced meniscus for meniscus regeneration. Kobayashi et al²¹ proposed the use of meniscus fragments as a cell source not requiring isolation and culture. Mincing the meniscus increases the tissue surface area, enabling cells that are essential in meniscal repair to migrate to defects and providing more space for proliferation.²⁰ We considered the meniscus adequate for meniscal regeneration because it contains cells, such as fibrochondrocytes, that are beneficial for tissue regeneration. In vivo, migrated cells from minced meniscus in atelocollagen gel showed comparably higher staining for Ki67 in all groups, indicating that the cells could proliferate. In addition, 11.3×10^4 cells per 10 mg meniscus fragment could migrate and proliferate in the gel. This demonstrates that minced meniscus could be a potential cell source for meniscus regeneration.

Scaffolds for meniscus tissue engineering can be categorized into four broad classes: synthetic polymers, hydrogels, natural matrices, or tissue-derived materials. Similar to cell sources, there is no consensus regarding the ideal materials for scaffolds for meniscal regeneration. However, it is important to know the material properties of each potential scaffold to select the most appropriate scaffold for the target environment.^{31,32} Collagen is often used as a scaffold for cartilage regeneration. Collagen gels have been used for in vivo cartilage regeneration experiments with some clinical applications.³³⁻³⁹ In our in vivo experiment, the minced meniscus and atelocollagen scaffold complex remained in the transplanted area for 12 weeks without deviation to the cavity of the knee joint, as observed in MRI. There was no significant difference between the defect and atelocollagen groups observed via macroscopic and histological analysis. Thus, the regenerated tissues in the minced meniscus group were not derived from the surrounding tissues but rather from the implanted minced meniscus. Atelocollagen may be an appropriate scaffold for implantation of minced meniscus owing to its ease of use and ability to restore tissue at the defect site. MSCs are widely accepted to have the potential to regenerate the meniscus; previously, MSCs from synovial tissues were found to contribute to meniscus regeneration.^{40,41} These cells have multidifferentiation capacity and recruit cellular and growth factors. Synovial cells also contribute to meniscus repair.⁴² In this study, the expression of MSC markers was not observed in the regeneration process until eight weeks. It was also confirmed that meniscus cells were capable of

chondrogenesis, suggesting that the meniscus cells from the fragment itself may contribute to the regenerated meniscus. Moreover, the in vitro study revealed that the migrated cells from the fragment have a high cell proliferation capacity. These cells may produce extracellular matrix in the gel during the process. It is also possible that the production of the extracellular matrix from the meniscus fibrochondrocytes from the fragments might be promoted by the surrounding synovium.

This study has some limitations. First, the mechanical properties of the regenerated tissue were not evaluated. However, the morphology of the regenerated tissue was similar to that of native meniscal tissue. Second, this study was based on a rabbit model; meniscal cell proliferation, matrix production, and the strength of meniscal tissue may differ between humans and rabbits. Third, the appropriate amount of minced meniscus for embedding in atelocollagen was not established. However, the amount of minced meniscus was unrelated to cell proliferation, as all groups exhibited similar cell growth. Fourth, the anterior half of the medial meniscus was excised to produce the massive meniscal defect, however, the defect area was not loaded with body weight. Further, the meniscal area loaded with body weight is larger in humans than in rabbits. Whether tissues can be regenerated in humans, as achieved in this study, is uncertain. Regardless, the proper scaffold material for implantation of the minced meniscus at the defect site is required.

In conclusion, this study showed that cells in the minced meniscus can proliferate and implantation of the minced meniscus within atelocollagen induced meniscus regeneration. Thus, this novel meniscus regeneration method may be a potential therapeutic alternative to a one-step surgery for treating meniscus tears.

Supplementary material

References

- Baker P, Coggon D, Reading I, Barrett D, McLaren M, Cooper C. Sports injury, occupational physical activity, joint laxity, and meniscal damage. *J Rheumatol*. 2002;29(3):557–563.
- Boyd KT, Myers PT. Meniscus preservation; rationale, repair techniques and results. *Knee*. 2003;10(1):1–11.
- Hennerbichler A, Moutos FT, Hennerbichler D, Weinberg JB, Guilak F. Repair response of the inner and outer regions of the porcine meniscus in vitro. *Am J Sports Med*. 2007;35(5):754–762.
- Rodeo SA. Cell therapy in orthopaedics: where are we in 2019? *Bone Joint J*. 2019;101-B(4):361–364.
- Wang J, Zhou L, Zhang Y, Huang L, Shi Q. Mesenchymal stem cells - a promising strategy for treating knee osteoarthritis. *Bone Joint Res*. 2020;9(10):719–728.
- Roos H, Laurén M, Adalberth T, Roos EM, Jonsson K, Lohmander LS. Knee osteoarthritis after meniscectomy: prevalence of radiographic changes after twenty-one years, compared with matched controls. *Arthritis Rheum*. 1998;41(4):687–693.
- Prockop DJ. Marrow stromal cells as stem cells for nonhematopoietic tissues. *Science*. 1997;276(5309):71–74.
- Yoshimura H, Muneta T, Nimura A, Yokoyama A, Koga H, Sekiya I. Comparison of rat mesenchymal stem cells derived from bone marrow, synovium, periosteum, adipose tissue, and muscle. *Cell Tissue Res*. 2007;327(3):449–462.
- Pittenger MF, Mackay AM, Beck SC, et al. Multilineage potential of adult human mesenchymal stem cells. *Science*. 1999;284(5411):143–147.
- Sakaguchi Y, Sekiya I, Yagishita K, Muneta T. Comparison of human stem cells derived from various mesenchymal tissues: superiority of synovium as a cell source. *Arthritis Rheum*. 2005;52(8):2521–2529.
- Horie M, Sekiya I, Muneta T, et al. Intra-Articular injected synovial stem cells differentiate into meniscal cells directly and promote meniscal regeneration without mobilization to distant organs in rat massive meniscal defect. *Stem Cells*. 2009;27(4):878–887.
- Osawa A, Harner CD, Gharaibeh B, et al. The use of blood vessel-derived stem cells for meniscal regeneration and repair. *Med Sci Sports Exerc*. 2013;45(5):813–823.
- Martinek V, Ueblacker P, Bräun K, et al. Second generation of meniscus transplantation: in-vivo study with tissue engineered meniscus replacement. *Arch Orthop Trauma Surg*. 2006;126(4):228–234.
- Kon E, Filardo G, Tschon M, et al. Tissue engineering for total meniscal substitution: animal study in sheep model—results at 12 months. *Tissue Eng Part A*. 2012;18(15-16):1573–1582.
- Zhu W-H, Wang Y-B, Wang L, Qiu G-F, Lu L-Y. Effects of canine myoblasts expressing human cartilage-derived morphogenetic protein-2 on the repair of meniscal fibrocartilage injury. *Mol Med Rep*. 2014;9(5):1767–1772.
- Lu Y, Dhanaraj S, Wang Z, et al. Minced cartilage without cell culture serves as an effective intraoperative cell source for cartilage repair. *J Orthop Res*. 2006;24(6):1261–1270.
- Christensen BB, Olesen ML, Lind M, Foldager CB. Autologous cartilage CHIP transplantation improves repair tissue composition compared with marrow stimulation. *Am J Sports Med*. 2017;45(7):1490–1496.
- Cole BJ, Farr J, Winalski CS, et al. Outcomes after a single-stage procedure for cell-based cartilage repair: a prospective clinical safety trial with 2-year follow-up. *Am J Sports Med*. 2011;39(6):1170–1179.
- Tsuyuguchi Y, Nakasa T, Ishikawa M, et al. The benefit of minced cartilage over isolated chondrocytes in atelocollagen gel on chondrocyte proliferation and migration. *Cartilage*. 2021;12(1):93–101.
- Dai Z, Li K, Chen Z, et al. Repair of avascular meniscal injuries using juvenile meniscal fragments: an in vitro organ culture study. *J Orthop Res*. 2013;31(10):1514–1519.
- Kobayashi Y, Yasuda K, Kondo E, et al. Implantation of autogenous meniscal fragments wrapped with a fascia sheath enhances fibrocartilage regeneration in vivo in a large harvest site defect. *Am J Sports Med*. 2010;38(4):740–748.
- Matsusaki M, Ochi M, Uchio Y, et al. Effects of basic fibroblast growth factor on proliferation and phenotype expression of chondrocytes embedded in collagen gel. *Gen Pharmacol*. 1998;31(5):759–764.
- Hatsushika D, Muneta T, Horie M, Koga H, Tsuji K, Sekiya I. Intraarticular injection of synovial stem cells promotes meniscal regeneration in a rabbit massive meniscal defect model. *J Orthop Res*. 2013;31(9):1354–1359.
- Bonasia DE, Marmotti A, Mattia S, et al. The Degree of Chondral Fragmentation Affects Extracellular Matrix Production in Cartilage Autograft Implantation: An In Vitro Study. *Arthroscopy*. 2015;31(12):2335–2341.
- Pauli C, Whiteside R, Heras FL, et al. Comparison of cartilage histopathology assessment systems on human knee joints at all stages of osteoarthritis development. *Osteoarthritis Cartilage*. 2012;20(6):476–485.
- Langer R, Vacanti JP. Tissue engineering. *Science*. 1993;260(5110):920–926.
- Kang S-W, Son S-M, Lee J-S, et al. Regeneration of whole meniscus using meniscal cells and polymer scaffolds in a rabbit total meniscectomy model. *J Biomed Mater Res A*. 2006;77(4):659–671.
- Kon E, Chiari C, Marcacci M, et al. Tissue engineering for total meniscal substitution: animal study in sheep model. *Tissue Eng Part A*. 2008;14(6):1067–1080.
- Yamasaki T, Deie M, Shinomiya R, Yasunaga Y, Yanada S, Ochi M. Transplantation of meniscus regenerated by tissue engineering with a scaffold derived from a rat meniscus and mesenchymal stromal cells derived from rat bone marrow. *Artif Organs*. 2008;32(7):519–524.
- Moutos FT, Guilak F. Functional properties of cell-seeded three-dimensionally woven poly(epsilon-caprolactone) scaffolds for cartilage tissue engineering. *Tissue Eng Part A*. 2010;16(4):1291–1301.
- Moriguchi Y, Tateishi K, Ando W, et al. Repair of meniscal lesions using a scaffold-free tissue-engineered construct derived from allogenic synovial MscS in a miniature swine model. *Biomaterials*. 2013;34(9):2185–2193.
- Filardo G, Petretta M, Cavallo C, et al. Patient-Specific meniscus prototype based on 3D bioprinting of human cell-laden scaffold. *Bone Joint Res*. 2019;8(2):101–106.
- Kim J, Cho H, Young K, Park J, Lee J, Suh D. In vivo animal study and clinical outcomes of autologous atelocollagen-induced chondrogenesis for osteochondral lesion treatment. *J Orthop Surg Res*. 2015;10:82.
- Chaiyinyo K, Oakes BW, Van Damme M-PI. The use of debrided human articular cartilage for autologous chondrocyte implantation: maintenance of

- chondrocyte differentiation and proliferation in type I collagen gels. *J Orthop Res*. 2004;22(2):446–455.
35. **Mimura T, Imai S, Kubo M, et al.** A novel exogenous concentration-gradient collagen scaffold augments full-thickness articular cartilage repair. *Osteoarthritis Cartilage*. 2008;16(9):1083–1091.
 36. **Andereya S, Maus U, Gavenis K, et al.** [First clinical experiences with a novel 3D-collagen gel (CaReS) for the treatment of focal cartilage defects in the knee]. *Z Orthop Ihre Grenzgeb*. 2006;144(3):272–280.
 37. **Ochi M, Uchio Y, Kawasaki K, Wakitani S, Iwasa J.** Transplantation of cartilage-like tissue made by tissue engineering in the treatment of cartilage defects of the knee. *J Bone Joint Surg Br*. 2002;84-B(4):571–578.
 38. **Furthmayr H, Timpl R.** Immunohistochemistry of collagens and procollagens. *Int Rev Connect Tissue Res*. 1976;7:61–99.
 39. **Pontz B, Meigel W, Rauterberg J, Kühn K.** Localization of two species specific antigenic determinants on the peptide chains of calf skin collagen. *Eur J Biochem*. 1970;16(1):50–54.
 40. **Kondo S, Muneta T, Nakagawa Y, et al.** Transplantation of autologous synovial mesenchymal stem cells promotes meniscus regeneration in aged primates. *J Orthop Res*. 2017;35(6):1274–1282.
 41. **Hatsushika D, Muneta T, Nakamura T, et al.** Repetitive allogeneic intraarticular injections of synovial mesenchymal stem cells promote meniscus regeneration in a porcine massive meniscus defect model. *Osteoarthritis Cartilage*. 2014;22(7):941–950.
 42. **Kim W, Onodera T, Kondo E, et al.** Which contributes to meniscal repair, the synovium or the meniscus? an in vivo rabbit model study with the freeze-thaw method. *Am J Sports Med*. 2020;48(6):1406–1415.

Author information:

- N. Matsubara
- M. Ishikawa, MD, PhD
- N. Adachi, MD, PhD
Department of Orthopaedic Surgery, Graduate School of Biomedical and Health Sciences, Hiroshima University, Hiroshima, Japan.
- T. Nakasa, MD, PhD, Medical Center for Translational and Clinical Research, Hiroshima University Hospital, Hiroshima, Japan.
- T. Tamura, PhD, Department of Radiology, Hiroshima University Hospital, Hiroshima, Japan.

Author contributions:

- N. Matsubara: Conceptualized and designed the study, Acquired, analyzed, and interpreted the data, Drafted and proofread the manuscript.
- T. Nakasa: Conceptualized and designed the study, Acquired, analyzed, and interpreted the data, Drafted and proofread the manuscript.
- M. Ishikawa: Acquired, analyzed, and interpreted the data, Drafted and proofread the manuscript.
- T. Tamura: Acquired, analyzed, and interpreted the data.
- N. Adachi: Drafted and proofread the manuscript, Gave final approval of the manuscript.

Funding statement:

- This work was supported by the Japan Agency for Medical Research and Development (grant number 18im0210816h0001).

ICMJE COI statement:

- N. Adachi reports consultancy payments from Japan Tissue Engineering and a grant from the Japanese government, unrelated to this article.

© 2021 Author(s) et al. This is an open-access article distributed under the terms of the Creative Commons Attribution Non-Commercial No Derivatives (CC BY-NC-ND4.0) licence, which permits the copying and redistribution of the work only, and provided the original author and source are credited. See <https://creativecommons.org/licenses/by-nc-nd/4.0/>.