

## Orbitally Driven Spin-Singlet Dimerization in $S = 1$ $\text{La}_4\text{Ru}_2\text{O}_{10}$

Hua Wu,<sup>1</sup> Z. Hu,<sup>1</sup> T. Burnus,<sup>1</sup> J. D. Denlinger,<sup>2</sup> P. G. Khalifah,<sup>3,4</sup> D. G. Mandrus,<sup>4</sup> L.-Y. Jang,<sup>5</sup> H. H. Hsieh,<sup>6</sup> A. Tanaka,<sup>7</sup> K. S. Liang,<sup>5</sup> J. W. Allen,<sup>8</sup> R. J. Cava,<sup>9</sup> D. I. Khomskii,<sup>1</sup> and L. H. Tjeng<sup>1</sup>

<sup>1</sup>*II. Physikalisches Institut, Universität zu Köln, Zùlpicher Straße 77, 50937 Köln, Germany*

<sup>2</sup>*Advanced Light Source, Lawrence Berkeley National Laboratory, Berkeley, California 94720, USA*

<sup>3</sup>*Department of Chemistry, University of Massachusetts, Amherst, Massachusetts 01003, USA*

<sup>4</sup>*Condensed Matter Sciences Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA*

<sup>5</sup>*National Synchrotron Radiation Research Center, 101 Hsin-Ann Road, Hsinchu 30077, Taiwan*

<sup>6</sup>*Chung Cheng Institute of Technology, National Defense University, Taoyuan 335, Taiwan*

<sup>7</sup>*Department of Quantum Matter, ADSM, Hiroshima University, Higashi-Hiroshima 739-8530, Japan*

<sup>8</sup>*Randall Laboratory of Physics, University of Michigan, Ann Arbor, Michigan 48109, USA*

<sup>9</sup>*Department of Chemistry, Princeton University, Princeton, New Jersey 08540, USA*

(Received 24 February 2006; published 30 June 2006)

Using x-ray absorption spectroscopy at the Ru- $L_{2,3}$  edge we reveal that the  $\text{Ru}^{4+}$  ions remain in the  $S = 1$  spin state across the rare  $4d$ -orbital ordering transition and spin-gap formation. We find using local spin density approximation + Hubbard U band structure calculations that the crystal fields in the low-temperature phase are not strong enough to stabilize the  $S = 0$  state. Instead, we identify a distinct orbital ordering with a significant anisotropy of the antiferromagnetic exchange couplings. We conclude that  $\text{La}_4\text{Ru}_2\text{O}_{10}$  appears to be a novel material in which the orbital physics drives the formation of spin-singlet dimers in a quasi-two-dimensional  $S = 1$  system.

DOI: [10.1103/PhysRevLett.96.256402](https://doi.org/10.1103/PhysRevLett.96.256402)

PACS numbers: 71.20.-b, 75.25.+z, 75.30.Et, 78.70.Dm

One of the most intriguing aspects of transition metal materials is the wide variety and richness of their physical properties [1]. Although conceptually clean and beautiful, theoretical simplifications in terms of a Heisenberg model or a single band Hubbard model turn out to be inadequate [2]. It now becomes more and more clear that a full identification of the relevant orbital and spin degrees of freedom of the ions involved is needed to understand, for instance, the colossal magnetoresistance behavior in the manganates [3–5], magnetization reversals, and metal-insulator transitions in early transition metal oxides [6–10], as well as the formation of spin gaps in non-one-dimensional  $S = \frac{1}{2}$  systems [11–14].

Very recently Khalifah *et al.* [15] synthesized the semi-conducting quasi-two-dimensional  $\text{La}_4\text{Ru}_2\text{O}_{10}$  compound and discovered that this system undergoes a strong first-order structural transition at  $T_s = 160$  K (see Fig. 1), accompanied by a rare  $4d$ -orbital ordering and spin-gap opening. Their interpretation of these phenomena was that the  $\text{Ru}^{4+}$  ion transforms from the usual  $t_{2g}^3 t_{2g}^1$  low-spin state with  $S = 1$  to an  $t_{2g}^2 t_{2g}^1$  “ultralow” spin state with  $S = 0$ , caused by a sufficiently strong crystal-field splitting (CFS) of the Ru  $4d$ - $t_{2g}$  levels due to the lattice distortion below  $T_s$ .

However, already soon after that, it was also hypothesized by Khalifah *et al.* based on unpublished standard band structure calculations that a chemical bond may be formed associated with the orbital ordering. Here we report on an x-ray absorption spectroscopy (XAS) study in which we reveal that the  $\text{Ru}^{4+}$  ions remain in the  $S = 1$  spin state across  $T_s$ . This directly points to the possibility that

$\text{La}_4\text{Ru}_2\text{O}_{10}$  is in fact a novel system in which the spin-gap opening is due to a singlet dimer formation in a non-one-dimensional and  $S > \frac{1}{2}$  material. We find using local spin density approximation + Hubbard U (LSDA + U) band structure calculations that the distinct orbital ordering involves a significant anisotropy of the antiferro-

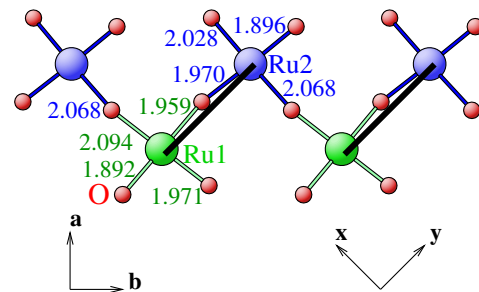


FIG. 1 (color online). The main block of the low-temperature (20 K) triclinic crystal structure of  $\text{La}_4\text{Ru}_2\text{O}_{10}$  shown in the crystallographic  $ab$  plane: the two-dimensional Ru-O network consisting of distorted  $\text{RuO}_6$  octahedra extends along the  $c$  axis (not shown, pointing into paper plane) and  $b$  axis with corrugation. The Ru-O bond lengths are marked in units of  $\text{Å}$ , and those out of the  $ab$  plane (not shown) are 2.046 and 2.057  $\text{Å}$  for Ru1, and 2.046 and 2.082  $\text{Å}$  for Ru2. The spin-singlet dimers are marked by black solid bars. The local orthogonal coordinate system ( $xyz$ ) is used in our band calculations with  $z$  parallel to  $c$  and  $y$  ( $x$ ) along the short (long) Ru1-Ru2 direction. The high-temperature monoclinic structure (not shown) above  $T_s = 160$  K has equal Ru-Ru distances along the  $x$  and  $y$  directions: Ru1 and Ru2 are equivalent.

magnetic exchange couplings, indicating indeed the formation of Ru ( $S = 1$ )-Ru ( $S = 1$ ) singlet dimers.

Floating zone crystals were grown in an NEC SC-M15HD image furnace using rods with a 1:1 or 4:5 ratio of La:Ru which had been prereacted and sintered in air at 1250 °C. A small (1–2 atm) overpressure of oxygen aided the growth, and the power was dynamically increased during the run to compensate for absorption by the copious amounts of evaporated Ru. Sizeable crystals could only be obtained using seed crystals. X-ray diffraction confirmed both the macroscopic phase purity and the universal presence of two twin domains. The XAS measurements were performed at the Taiwan NSRRC 15B beam line, equipped with a double Si(111) crystal monochromator delivering photons from 2 keV and up. The spectra were recorded using the total electron yield method in a chamber with a base pressure in the low  $10^{-10}$  mbar range. Clean sample areas were obtained by cleaving the crystals *in situ*. The photon energy resolution at the Ru  $L_{2,3}$  edges ( $h\nu \approx 2.9$  keV) was set at 0.6 eV. Strong polarization dependent O-K XAS spectra [16] verify the high sample quality.

The top curves of Fig. 2 depict the Ru- $L_{2,3}$  XAS spectra of  $\text{La}_4\text{Ru}_2\text{O}_{10}$  taken at 220 K (black line) and 110 K (red line). The spectral line shapes depend strongly on the multiplet structure given by the Ru  $4d$ - $4d$  and  $2p$ - $4d$  Coulomb and exchange interactions, as well as by the local CFS and the hybridization with the O  $2p$  ligands. Unique to XAS is that the dipole selection rules are very effective in determining which of the  $2p^5 4d^{n+1}$  final states can be reached and with what intensity, starting from a particular  $2p^6 4d^n$  initial state ( $n = 4$  for  $\text{Ru}^{4+}$ ) [17,18]. This makes the technique extremely sensitive to the quantum numbers of the initial state [19,20].

The essence of the Ru- $L_{2,3}$  XAS spectra in Fig. 2 is that there is only a very small change across  $T_s$ , suggesting that the local electronic and spin state of the  $\text{Ru}^{4+}$  ion in the high-temperature (HT) and low-temperature (LT) phases

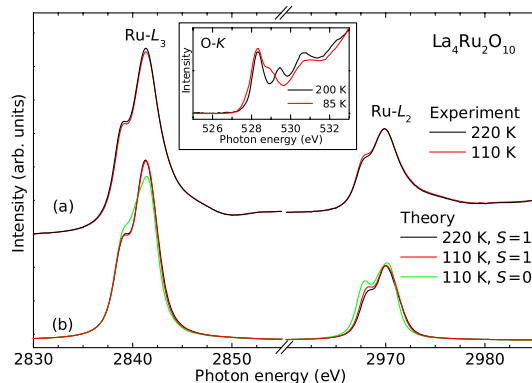


FIG. 2 (color online). (a) Experimental Ru- $L_{2,3}$  XAS spectra of  $\text{La}_4\text{Ru}_2\text{O}_{10}$  measured at 220 and 110 K, i.e., above and below  $T_s = 160$  K. (b) Theoretical simulations for the  $\text{Ru}^{4+}$  ion in the  $S = 1$  high-temperature phase at 220 K,  $S = 1$  low-temperature phase at 110 K, and  $S = 0$ . The inset shows O-K spectra measured at 200 and 85 K from [16].

are quite similar. This seems surprising in view of the fact that we observed considerable modifications in the O-K XAS spectra in going from 200 K (black line) to 85 K (red line) as shown in the inset of Fig. 2 [16]. Since these O-K spectra are known to be sensitive to band structure effects [17], their modifications are fully consistent with the strong changes in the crystal structure as seen in neutron diffraction [15], confirming the good quality of our samples.

To extract quantitative information on the CFS and spin state from the Ru spectra, we have performed simulations using the successful configuration interaction cluster model [17,18,21]. The calculations have been carried out for a  $\text{RuO}_6$  cluster in the proper HT and LT local coordination using the XTLS 8.3 program [21]. Parameters for the multipole part of the Coulomb interactions were set standardly at 80% of the Hartree-Fock values [21], while the monopole parts ( $U_{dd}$ ,  $U_{pd}$ ) were taken from  $\text{Ca}_2\text{RuO}_4$  [22,23]. The O  $2p$ -Ru  $4d$  charge transfer energy was estimated from LDA calculations (see below), and the O  $2p$ -Ru  $4d$  transfer integrals and their distance dependence from Harrison's relations [24]. The local CFS parameters are to be determined from the comparison between the simulations and the experimental spectra.

The bottom curves of Fig. 2 show the simulations for both the HT and LT phases. We found optimal fits (black and red lines) if the Ru- $4d$   $xz$  orbital is set at about 100–150 meV (HT) and 200–300 meV (LT) lower in energy than the essentially degenerate (within 50 meV)  $yz$  and  $xy$  orbitals [25]. These numbers refer to total energies calculated including the CFS and covalency but without spin-orbit interaction. Important is that the cluster calculation indeed finds the  $S = 1$  state for both the HT and LT phases, which is a direct consequence of the fact that in both phases the  $xz$  orbital is essentially doubly occupied while the  $yz$  and  $xy$  are each singly occupied. We also have carried out calculations for the Ru ion in the artificial  $S = 0$  state by changing the CFS parameter such that the  $xz$  orbital lies above the degenerate  $yz$  and  $xy$  orbitals [25]. As shown in Fig. 2, the simulated spectrum (green curve) disagrees with the experiment. So we can rule out that the spin-gap opening is due to a local spin state transition [15].

To confirm our XAS-derived conclusions and, more importantly, to get in-depth understanding of the nature of the spin-gap state below  $T_s$ , we performed systematic LDA and LSDA + U band structure calculations [26], by using the full-potential augmented plane waves plus local orbital method [27]. We took the neutron crystal structure data at 20 K and 298 K [15]. The muffin-tin sphere radii are chosen to be 2.8, 2.0, and 1.5 Bohr for La, Ru, and O atoms, respectively.  $U = 3$  eV and Hund's rule exchange  $J_H = 0.5$  eV ( $U_{\text{eff}} = 2.5$  eV) are used for Ru  $4d$  electrons, which are common for ruthenates [22,28,29].

Figure 3 shows the Ru  $4d$  density of states (DOS) calculated using the LDA for the nonmagnetic (NM) state. The inset shows a close-up of the  $t_{2g}$  levels and a calculation of the first moments supports the XAS analysis: for

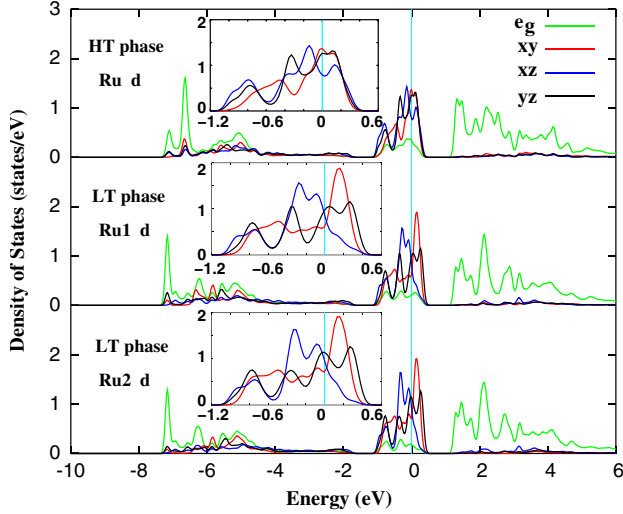


FIG. 3 (color online). LDA density of states of the Ru  $4d$  orbitals in the high-temperature (HT, upper panel) and low-temperature (LT, middle and lower panels) phases. The insets show a close-up of the  $t_{2g}$  ( $xy$ ,  $xz$ , and  $yz$ ) states in the vicinity of the Fermi level set at 0 eV.

both the HT and LT phases, the  $xz$  orbital lies lowest and the splitting  $\Delta'_{CF}$  between the higher lying  $yz$  and  $xy$  orbitals is less than 50 meV. It is the magnitude of this  $\Delta'_{CF}$  relative to  $J_H$  which determines the spin state of the  $Ru^{4+}$  ion. To make a crude estimate: the  $S = 1$  state ( $xz^{\uparrow}yz^{\uparrow}xy^{\downarrow}$ ) carries the Hund's stabilization energy of  $3J_H$ , whereas the  $S = 0$  state ( $xz^{\uparrow}yz^{\uparrow}$ ) has a total stabilization energy of  $2J_H$  plus  $\Delta'_{CF}$ . Assuming that 0.5 eV is a reasonable estimate for  $J_H$ , one must expect that a  $\Delta'_{CF}$  of 0.05 eV is far from sufficient to obtain the  $S = 0$  state. Obviously this is what the XAS experiments have revealed. Moreover, our LDA calculations also find that the ferromagnetic (FM) as well as the antiferromagnetic (AF) solution are more stable than the NM one, giving further support that the  $S = 0$  is unfavorable. This was also found recently by LDA calculations of Eyert *et al.* [30].

The LDA results as shown in Fig. 3 predict a metallic state for both the HT and LT phases, and this is in strong disagreement with the observed semiconducting behavior with a gap of about 0.3 eV [15]. One should note, however, that the Fermi level is located in a narrow Ru  $t_{2g}$  band with

no more than 1.5 eV width. This signals that modest electron correlation effects at the Ru sites will already be able to turn this material into a Mott insulator. We therefore set out to do LSDA + U calculations for the LT phase and found that a band gap of about 0.5 eV is indeed opened in the Ru  $t_{2g}$  band as can be seen from Fig. 4(a). Within the LSDA + U mean-field approach, the lowest state of this insulator is AF and is labeled as AF $_{xyz}$  in Table I to indicate the AF alignment with the nearest neighbors along the  $x$ ,  $y$ , and  $z$  directions (Fig. 1). The  $Ru^{4+}$  spin moment inside the muffin-tin sphere is about  $1.2 \mu_B$ , confirming the XAS result that the spin state is  $S = 1$  but not  $S = 0$ .

It is important to look now at the orbital character of the AF $_{xyz}$  solution. Figures 4(b) and 4(c) show the orbitally resolved DOS of the AF aligned Ru1 and Ru2 ions. One can clearly see for each of the ions that the  $xy$  and  $yz$  orbitals (with the spins parallel) are singly occupied while the  $xz$  are doubly occupied. This double occupation is due to the Ru-O bonds being elongated along the  $x$  direction, see Fig. 1. We thus find an orbital ordered state which is different from the originally proposed doubly occupied  $xy$  and  $xz$  ( $S = 0$ ) state [15].

As a result, the half-filled  $xy$  and  $yz$  orbitals are magnetically active. To explain the formation of the spin gap in the LT phase, it is crucial to identify the relevant exchange interactions in this system. We therefore have calculated other magnetic configurations: the FM and two more types of AF solutions, namely AF $_{xy}$  and AF $_{yz}$ . The  $2 \times La_4Ru_2O_{10}$  unit cell is used for all solutions, except for AF $_{yz}$  where the  $4 \times La_4Ru_2O_{10}$  unit cell is taken with the doubling along the  $b$  direction (see Fig. 1). We also studied the NM solution, and confirmed that this is much higher in energy than the AF $_{xyz}$ , by 775 meV per formula unit (Table I). The NM solution is metallic, the FM half-metallic, and all AF insulating. The  $Ru^{4+}$  spin moment is  $1.2 \pm 0.1 \mu_B$  for all magnetic solutions.

The relative energies of the different magnetic states allow us to estimate the exchange constants  $J_x$ ,  $J_y$ , and  $J_z$  along the  $x$ ,  $y$ , and  $z$  directions (Fig. 1), respectively. With the FM being 130–150 meV higher in energy than the AF solutions, we thus have very large AF exchange interactions in this system. As listed in Table I, we find  $J_x = 1.5$  meV,  $J_y = 65.5$  meV, and  $J_z = 4.5$  meV. The signifi-

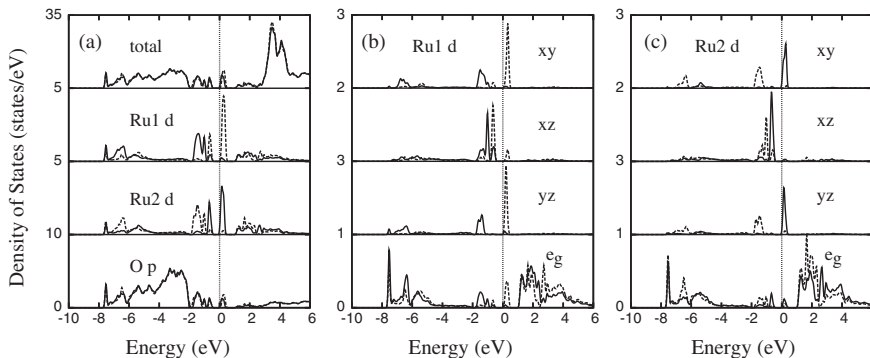


FIG. 4. Density of states (DOS) of the  $La_4Ru_2O_{10}$  in the antiferromagnetic low-temperature phase calculated using LSDA + U. (a) Total DOS per formula unit, the  $4d$  states of the two inequivalent  $Ru^{4+}$  ions, and the  $2p$  states of all the ten oxygens; (b) orbitally resolved  $4d$  states of Ru1 and (c) of Ru2. The solid (dashed) curves denote the up- (down)-spin channels.

TABLE I. LSDA + U results for the total energy (per formula unit and relative to the lowest solution) and band gap in the low-temperature phase of  $\text{La}_4\text{Ru}_2\text{O}_{10}$ , calculated for the nonmagnetic (NM), ferromagnetic (FM), and three types of antiferromagnetic (AF) solutions. The exchange constants are found to be  $J_x = 1.5$  meV,  $J_y = 65.5$  meV, and  $J_z = 4.5$  meV.

State	Exchange	Energy (meV)	Gap (eV)
NM	...	775	...
FM	$J_x + J_y + 2J_z$	152	...
AF <sub>xyz</sub>	$-J_x - J_y - 2J_z$	0	0.5
AF <sub>xy</sub>	$-J_x - J_y + 2J_z$	18	0.3
AF <sub>yz</sub>	$J_x - J_y - 2J_z$	3	0.4

cant anisotropy is related to the fact that *both* the *xy* and *yz* orbitals contribute to the exchange coupling along the *y* direction having the *short* Ru-O-Ru distance, while *only* the *xy* or *yz* orbital contributes to the *x* or *z* direction, respectively, having the *long* Ru-O-Ru distance. Hence we can consider the LT phase of  $\text{La}_4\text{Ru}_2\text{O}_{10}$  as practically consisting of strongly coupled Ru-Ru dimers with weak interdimer coupling, or at most as two-leg ladders with  $J_{\text{rung}} = J_y = 65.5$  meV and  $J_{\text{leg}} = J_z = 4.5$  meV, with weak interladder coupling of 1.5 meV. Those rather well isolated Ru-Ru dimers or rungs will have the singlet ground state [31]. This explains naturally the appearance of a spin gap in the LT phase, which, according to our calculations, should be about 60 meV, in reasonable agreement with the measured value of 40 meV [15]. The dimer character of the spin gap seems also to agree with the results of the single-crystal neutron scattering [32].

To summarize, XAS measurements revealed that the  $\text{Ru}^{4+}$  ions in  $\text{La}_4\text{Ru}_2\text{O}_{10}$  remain in the  $S = 1$  spin state across the structural phase transition and spin-gap formation. LSDA + U calculations provided support for this finding and identified the distinct orbital ordering accompanying the structural transition. Crucial is that with LSDA + U we were able to estimate the intersite antiferromagnetic exchange interactions and found them to be highly anisotropic. This brought us to the conclusion that the spin-gap opening is due to the formation of Ru-Ru singlet dimers. Such a transition is rather unusual since  $\text{La}_4\text{Ru}_2\text{O}_{10}$  is a two-dimensional  $S = 1$  system; it is largely driven by orbital ordering which amplifies the importance of orbital physics in correlated systems.

We acknowledge the NSRRC for the extremely stable beam. We thank M. W. Haverkort for valuable discussions and Lucie Hamdan for her skillful technical assistance. The research in Cologne is supported by the Deutsche Forschungsgemeinschaft through SFB 608 and by the European project COMEPHS, and the research in the US by DOE Contract No. DE-AC05-00OR22725.

- [1] M. Imada, A. Fujimori, and Y. Tokura, Rev. Mod. Phys. **70**, 1039 (1998).
- [2] Y. Tokura and N. Nagaosa, Science **288**, 462 (2000).
- [3] A. P. Ramirez, J. Phys. Condens. Matter **9**, 8171 (1997).
- [4] D. I. Khomskii and G. A. Sawatzky, Solid State Commun. **102**, 87 (1997).
- [5] T. Mizokawa and A. Fujimori, Phys. Rev. B **51**, 12 880 (1995); **54**, 5368 (1996); **56**, R493 (1997).
- [6] Y. Ren *et al.*, Nature (London) **396**, 441 (1998).
- [7] G. R. Blake *et al.*, Phys. Rev. Lett. **87**, 245501 (2001).
- [8] C. Ulrich *et al.*, Phys. Rev. Lett. **91**, 257202 (2003).
- [9] J.-H. Park *et al.*, Phys. Rev. B **61**, 11 506 (2000).
- [10] M. W. Haverkort *et al.*, Phys. Rev. Lett. **95**, 196404 (2005).
- [11] M. Isobe *et al.*, J. Phys. Soc. Jpn. **71**, 1423 (2002).
- [12] P. G. Radaelli *et al.*, Nature (London) **416**, 155 (2002).
- [13] M. Schmidt *et al.*, Phys. Rev. Lett. **92**, 056402 (2004).
- [14] D. I. Khomskii and T. Mizokawa, Phys. Rev. Lett. **94**, 156402 (2005).
- [15] P. Khalifah *et al.*, Science **297**, 2237 (2002).
- [16] J. D. Denlinger *et al.* (to be published).
- [17] F. M. F. de Groot, J. Electron Spectrosc. Relat. Phenom. **67**, 529 (1994).
- [18] See the Theo Thole Memorial Issue, J. Electron Spectrosc. Relat. Phenom. **86**, 1 (1997).
- [19] Z. Hu *et al.*, Phys. Rev. B **61**, 5262 (2000).
- [20] Z. Hu *et al.*, Phys. Rev. Lett. **92**, 207402 (2004).
- [21] A. Tanaka and T. Jo, J. Phys. Soc. Jpn. **63**, 2788 (1994).
- [22] T. Mizokawa *et al.*, Phys. Rev. Lett. **87**, 077202 (2001); Phys. Rev. B **69**, 132410 (2004).
- [23] Both  $\text{La}_4\text{Ru}_2\text{O}_{10}$  and  $\text{Ca}_2\text{RuO}_4$  are two dimensional and have almost the same octahedral  $\langle \text{Ru}^{4+} - \text{O} \rangle$  bond lengths and similar  $t_{2g}$  bandwidths of about 1.5 eV.
- [24] W. A. Harrison, *Electronic Structure and the Properties of Solids* (Dover, New York, 1989).
- [25] Parameters for  $\text{RuO}_6$  cluster [eV]:  $U_{dd} = 3.0$ ,  $U_{cd} = 2.0$ ,  $\Delta = 2.0$ ,  $pd\sigma = -2.1$  for 2.01 Å,  $10Dq = 1.9$ ,  $Dt = 0.04$ ,  $Du = 0.04$ ,  $Dv = 0.00$ ,  $\zeta = 60\%$  of Hartree-Fock value;  $Ds = -0.03$  ( $S = 1$ , HT),  $-0.06$  ( $S = 1$ , LT),  $+0.90$  ( $S = 0$ , LT).
- [26] V. I. Anisimov *et al.*, Phys. Rev. B **48**, 16 929 (1993).
- [27] P. Blaha *et al.*, <http://www.wien2k.at>.
- [28] Z. Fang, N. Nagaosa, and K. Terakura, Phys. Rev. B **69**, 045116 (2004).
- [29] Using a larger Hubbard  $U = 5$  eV does not change the spin-singlet dimer picture at all, but gives a too large band gap of 1.1 eV.
- [30] V. Eyert, S. G. Ebbinghaus, and T. Kopp, Phys. Rev. Lett. **96**, 256401 (2006).
- [31] Inclusion of the spin-orbit coupling does not affect our conclusions: the *xz* orbital in the LT phase being lower than the *yz* and *xy* by the CFS of  $\approx 300$  meV together with the band formation make the weaker spin-orbit coupling of  $\approx 150$  meV to be less operative. The exchange constants change by less than 5 meV and the orbital moment is small, not more than about  $0.2 \mu_B$ .
- [32] R. Osborn (private communication).