

## Exchange splittings of Mn- and Sb-derived states by spin-resolved valence-band photoemission of MnSb

Oliver Rader\*

*Department of Physics, University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113, Japan*

Akio Kimura, Nozomu Kamakura, Ki-Seok An, and Akito Kakizaki

*Institute for Solid State Physics (ISSP), University of Tokyo, 7-22-1 Roppongi, Minato-ku, Tokyo 106, Japan*

Shintaro Miyanishi and Hiroyuki Akinaga

*Joint Research Center for Atom Technology, National Institute for Advanced Interdisciplinary Research (JRCAT-NAIR), 1-1-4 Higashi, Tsukuba, Ibaraki 305, Japan*

Masafumi Shirai

*Department of Physical Science, Graduate School of Engineering Science, Osaka University, 1-3 Machikaneyama-cho, Toyonaka 560, Japan*

Kenya Shimada and Atsushi Fujimori

*Department of Physics, University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113, Japan*

(Received 8 October 1997)

We have grown epitaxial (0001)-oriented films of the ferromagnetic intermetallic compound MnSb on GaAs(111) substrates. The *ex situ* grown samples can be reprepared in such a way that clean, ordered, and magnetically saturated surfaces are obtained. Using spin-resolved photoemission, Sb5*p*- and Mn3*d*-derived spectral features are identified, and large exchange splittings (1.4 and 1.7 eV for Mn-Sb bonding states and about 3.0 eV for Mn nonbonding states) are measured. Our *ab initio* band-structure calculation agrees rather well with the experiment, reproducing the exchange splittings of Mn-Sb states but slightly underestimating that of Mn states. [S0163-1829(98)50802-8]

Progress in various research areas has in the past years rendered the ferromagnetic manganese monopnictides MnAs, MnSb, and MnBi prime candidates for materials of novel electronic devices: Large Kerr rotation angles, needed in magneto-optical recording, have been measured for MnBi (Ref. 1) and MnSb5%Pt.<sup>2</sup> Both MnSb and MnBi have a large magnetic moment and a Curie temperature well above room temperature (e.g., MnSb:  $\mu = 3.5\mu_B$  and  $T_C = 585$  K; see Ref. 3). The hexagonal crystal structure [NiAs type, Fig. 1(b)] is favorable for obtaining uniaxial magnetocrystalline anisotropies, and it has already been achieved to induce perpendicular magnetic anisotropy, which is desired in recording devices, in films of MnSb<sub>1-x</sub>Bi<sub>x</sub>.<sup>2</sup> MnSb has been studied by magnetic circular x-ray dichroism, and a substantial orbital magnetic moment was found.<sup>4</sup> Very recently, epitaxial growth of MnAs (Ref. 5) and MnSb (Ref. 6) films on GaAs crystals has become possible, thus enabling the integration of ferromagnetic storage into semiconductor devices.

The various theoretical approaches to the electronic structure of MnSb have been reviewed in Ref. 3. In brief, ionic-like models and alloylike models for different degrees of hybridization between Mn and Sb electronic states have been proposed. Recently, several calculations employing a band-structure model were conducted.<sup>3,7</sup> However, these predictions have never been tested by angle-resolved photoemission, and comparison to experimental data was limited to magnetic-moment and specific-heat measurements. Valence band x-ray photoemission<sup>8</sup> was only of limited benefit as it

was found to be in agreement both with a simple superposition of spectra of pure Mn and Sb in Ref. 8 and with a band calculation predicting a large Mn moment and strong Mn3*d*-Sb5*p* hybridization in Ref. 3.

Using spin- and angle-resolved photoemission, we want to verify experimentally which model of the electronic structure is appropriate. The experiment on MnSb is particularly challenging from the preparative point of view because of the limited probing depth of the experiment (a few atomic layers) and the possibility of losing the large Mn magnetic moment and the ferromagnetic coupling of these moments in the probed surface area if that should deviate from the ideal MnSb crystal structure. It will be seen that it is possible to obtain well-ordered and magnetically saturated surfaces and that analysis of the spin is indeed essential in order to assign spectral features and to verify in this way the complicated electronic structure of MnSb.

MnSb(0001) films in the  $\mu\text{m}$  thickness range were grown onto GaAs(111) in a molecular beam epitaxy chamber at JRCAT. Characterization during the growth was done using reflection high-energy electron diffraction and Auger electron spectroscopy. Growth parameters were similar to the ones published in Ref. 6. The samples were capped with Sb and exposed to air during transport to the beamline. Sample surfaces were reprepared by Ne<sup>+</sup> ion bombardment and annealing cycles until an intense and sharp hexagonal low-energy electron diffraction pattern became visible indicating a well-ordered surface. It was verified by Auger spectroscopy

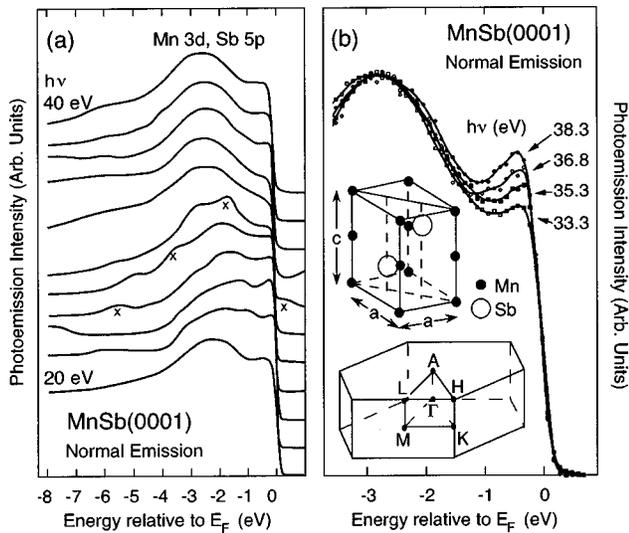


FIG. 1. (a) Angle-resolved photoemission spectra between 20 eV and 40 eV photon energy in steps of 2 eV. Light polarization is mixed  $s + p$ . Intensity induced by second-order light is marked. (b) Selected spectra for mainly  $s$ -polarized light near  $\Gamma$ . The spectra are consistent with a minority-spin band crossing  $E_F$  on the way from  $A$  to  $\Gamma$ . Crystal structure (NiAs type) of MnSb and bulk Brillouin zone are also given.

copy and photoemission at low photon energies that carbon and oxygen contaminations had completely been removed. Samples were remanently magnetized by applying a magnetic pulse in the film plane. We verified with magneto-optical Kerr effect that the remanent magnetization was almost 100% of the saturation magnetization. Spin- and angle-resolved photoemission measurements have been performed using linearly polarized light from the revolver undulator beamline<sup>9</sup> 19A of ISSP at Photon Factory, Tsukuba, for excitation and a 100-keV Mott detector<sup>10</sup> for spin analysis. The light was predominantly  $s$  polarized ( $18^\circ$  off-normal incidence). Angle-resolved photoemission spectra were also taken at beamline 18A with mixed ( $s$  and  $p$ ) polarization ( $45^\circ$  incidence). The vacuum was between  $1$  and  $2 \times 10^{-10}$  Torr, and the sample was cooled to  $\text{LN}_2$  temperature during spin-resolved measurements.

The appropriate photon energies for probing the electronic structure of MnSb lie below the  $3p$ - $3d$  resonant excitation threshold of Mn (50 eV). We measured angle-resolved photoemission spectra between  $h\nu = 20$  eV and 40 eV [Fig. 1(a)]. Emission was found to extend from  $E_F$  down to about 6 eV, assigned to Sb  $5p$  and Mn  $3d$  states and 10–11 eV assigned to Sb  $5s$  states (not shown). However, a clear separation of Mn $3d$ - and Sb $5p$ -derived spectral features appears difficult, possibly due to substantial hybridization between these orbitals.

Figure 2 shows spin-resolved photoelectron spectra. For 25.8 eV and 38.2 eV photon energies we expect to probe bulk initial states near the  $A$  and  $\Gamma$  points, respectively [see the Brillouin zone in Fig. 1(b)].<sup>11</sup> The spectrum at the bottom, measured at 25.8 eV photon energy, displays large differences between the majority- (upward triangles) and the minority-spin channel (downward triangles), proving ferromagnetic order in the surface region of the sample. In detail, there appears a single peak in the minority spectrum at  $-2.0$

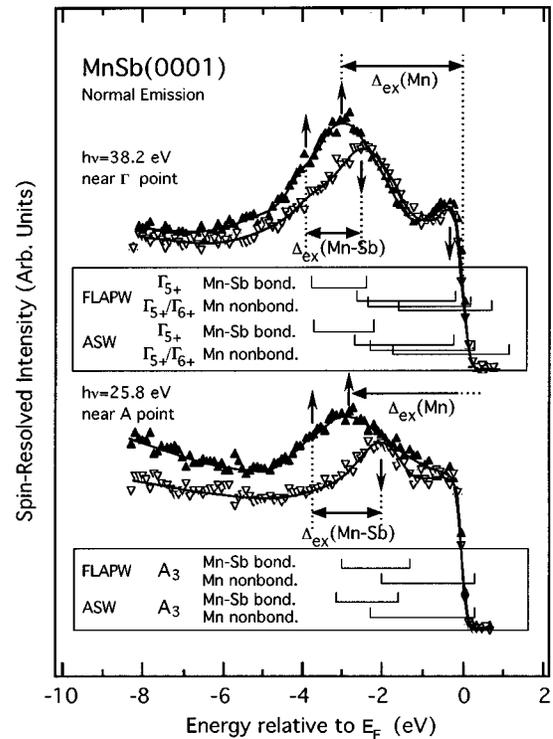


FIG. 2. Spin- and angle-resolved photoemission spectra of MnSb(0001). Upward triangles denote majority spin, downward triangles minority spin. Spectral features corresponding to exchange-split pairs of states are indicated. In addition, predictions for energy positions of exchange split states from this work (FLAPW) and Ref. 3 (ASW) are given.

eV and a broader peak ( $\approx -2.8$  eV) with a low-energy shoulder ( $\approx -3.7$  eV) in the majority spectrum. We expect Sb-derived emission to be less intense than Mn emission because the photoionization cross section favors Mn $3d$  over Sb $5p$  at this photon energy.<sup>12</sup> The structures in each spin channel with lowest energy, i.e., the majority-spin shoulder at  $-3.7$  eV and the minority-spin peak at  $-2.0$  eV, are of comparable intensity and smaller than the main majority-spin peak. Their energy separation, 1.7 eV, is incompatible with pure Mn $3d$  states in view of the large measured Mn moment of  $3.5\mu_B$ , and they are for this reason assigned as exchange-split states with substantial Sb $5p$  character. The maximum of the intense peak centered around  $-2.8$  eV is, on the other hand, assigned to Mn $3d$ . As a second intense minority spin peak is absent, the spectrum suggests that the Mn exchange splitting is very large ( $>2.8$  eV), so that the corresponding minority-spin state is unoccupied.<sup>13</sup>

This interpretation is corroborated by our electronic structure calculations from first principles using the full-potential linearized augmented plane wave (FLAPW) method:<sup>14</sup> In Fig. 3 we have highlighted Mn-Sb bonding states (dashed) and Mn nonbonding states (solid). For symmetry reasons<sup>15</sup> we expect in the present setup along  $[0001]$  ( $\Gamma$ - $A$ - $A$  direction) emission from  $\Lambda_5$  and  $\Lambda_6$  initial states. The band structure shows that the  $A$  point is fortunate for determining the exchange splitting since  $\Lambda_5$  and  $\Lambda_6$  states are degenerate here and, for minority spin, emission from only one initial state ( $A_3$  symmetry) is expected.

Towards  $\Gamma$ , the  $\Lambda_5$  bands disperse to lower energies. This



- \*Electronic address: rader@exp.bessy.de
- <sup>1</sup>K. Egashira and T. Yamada, *J. Appl. Phys.* **45**, 3643 (1974).
- <sup>2</sup>M. Takahashi, H. Shoji, Y. Hozumi, and T. Wakiyama, *J. Magn. Magn. Mater.* **131**, 67 (1994).
- <sup>3</sup>R. Coehoorn, C. Haas, and R. A. de Groot, *Phys. Rev. B* **31**, 1990 (1985). Eigenvalues quoted here were taken from Fig. 4.
- <sup>4</sup>A. Kimura, S. Suga, S. Imada, T. Muro, T. Shishidou, S. Y. Park, T. Miyahara, T. Kaneko, and T. Kanomata, *J. Electron Spectrosc. Relat. Phenom.* **78**, 287 (1996); *Phys. Rev. B* **56**, 6021 (1997).
- <sup>5</sup>M. Tanaka, J. P. Harbison, M. C. Park, Y. S. Park, T. Shin, and G. M. Rothberg, *Appl. Phys. Lett.* **65**, 1964 (1994).
- <sup>6</sup>H. Akinaga, Y. Suzuki, K. Tanaka, K. Ando, and T. Katayama, *Appl. Phys. Lett.* **67**, 141 (1995); H. Akinaga, K. Tanaka, K. Ando, and T. Katayama, *J. Cryst. Growth* **150**, 1144 (1995).
- <sup>7</sup>K. Motizuki, *J. Magn. Magn. Mater.* **70**, 1 (1987).
- <sup>8</sup>K. S. Liang and T. Chen, *Solid State Commun.* **23**, 975 (1977).
- <sup>9</sup>A. Kakizaki, H. Ohkuma, T. Kinoshita, A. Harasawa, and T. Ishii, *Rev. Sci. Instrum.* **63**, 367 (1992).
- <sup>10</sup>J. Fujii, T. Kinoshita, K. Shimada, T. Ikoma, A. Kakizaki, T. Ishii, H. Fukutani, A. Fujimori, K. Soda, H. Sugawara, in *Proceedings of the International Symposium on High Energy Spin Physics*, edited by T. Hasegawa, N. Horikawa, A. Masaïke, and S. Sawada (Universal Academy Press, Tokyo, 1992), p. 885.
- <sup>11</sup>Critical-point energies could not ambiguously be extracted from angle-resolved photoemission spectra. Therefore,  $\mathbf{k}_{\perp}$  was estimated with free-electron parabolas assuming an inner potential of  $-10$  eV and a work function of 4.5 eV. For initial states of  $-3$  eV,  $A$  and  $\Gamma$  points are predicted at 25.6 eV and 37.9 eV photon energy, respectively.
- <sup>12</sup>Photoionization cross sections vary strongly in the photon energy range studied here. Ratios, calculated for the atom, of  $Mn3d$  vs  $Sb5p$  cross sections are 5.12 at 25.8 eV and 22.70 at 38.2 eV [J.-J. Yeh, *Atomic Calculation of Photoionization Cross-Sections and Asymmetry Parameters* (Gordon and Breach, New York, 1993)].
- <sup>13</sup>There is also some intensity closer to the Fermi level (around  $-1$  eV for majority spin and around  $E_F$  for minority spin). This intensity was found to depend on annealing conditions and is therefore not thought of as representative of stoichiometric bulk MnSb.
- <sup>14</sup>For details of the calculations, see M. Shirai and Y. Tokioka, *J. Electron Spectrosc. Relat. Phenom.* (to be published).
- <sup>15</sup>F. J. Himpsel and D. E. Eastman, *Phys. Rev. B* **21**, 3207 (1980).
- <sup>16</sup>A. Santoni and F. J. Himpsel, *Phys. Rev. B* **43**, 1305 (1991).
- <sup>17</sup>K. Mimura, H. Sato, S. Senba, H. Namatame, and M. Taniguchi, *Physica B* **237-238**, 392 (1997).
- <sup>18</sup>O. Rader, W. Gudat, C. Carbone, E. Vescovo, S. Blügel, R. Kläs-ges, W. Eberhardt, M. Wuttig, J. Redinger, and F. J. Himpsel, *Phys. Rev. B* **55**, 5405 (1997).
- <sup>19</sup>R. A. de Groot, F. M. Mueller, P. G. van Engen, and K. H. J. Buschow, *Phys. Rev. Lett.* **50**, 2024 (1983).